

Chapter 10: Superconductivity

Bardeen, Cooper, & Schrieffer

April 26, 2017

Contents

1	Introduction	3
1.1	Evidence of a Phase Transition	3
1.2	Meissner Effect	4
2	The London Equations	8
3	Cooper Pairing	11
3.1	The Retarded Pairing Potential	11
3.2	Scattering of Cooper Pairs	13
3.3	The Cooper Instability of the Fermi Sea	15
4	The BCS Ground State	17
4.1	The Energy of the BCS Ground State	18
4.2	The BCS Gap	23
5	Consequences of BCS and Experiment	28
5.1	Specific Heat	28
5.2	Microwave Absorption and Reflection	29
5.3	The Isotope Effect	32

6	BCS \Rightarrow Superconducting Phenomenology	33
7	Coherence of the Superconductor \Rightarrow Meisner effects	38
8	Quantization of Magnetic Flux	41
9	Tunnel Junctions	43
10	Unconventional Superconductors	48
10.1	D-wave Superconductors	49
10.2	Triplet Superconductors	53
10.3	Odd-frequency Superconductors	54

1 Introduction

From what we have learned about transport, we know that there is no such thing as an ideal ($\rho = 0$) conventional conductor. All materials have defects and phonons (and to a lesser degree of importance, electron-electron interactions). As a result, from our basic understanding of metallic conduction ρ must be finite, even at $T = 0$. Nevertheless many superconductors, for which $\rho = 0$, exist. The first one Hg was discovered by Onnes in 1911. It becomes superconducting for $T < 4.2^\circ K$. Clearly this superconducting state must be fundamentally different than the "normal" metallic state. I.e., the superconducting state must be a different phase, separated by a phase transition, from the normal state.

1.1 Evidence of a Phase Transition

Evidence of the phase transition can be seen in the specific heat (See Fig. 1). The jump in the superconducting specific heat C_s indicates that there is a phase transition without a latent heat (i.e. the transition is continuous or second order). Furthermore,

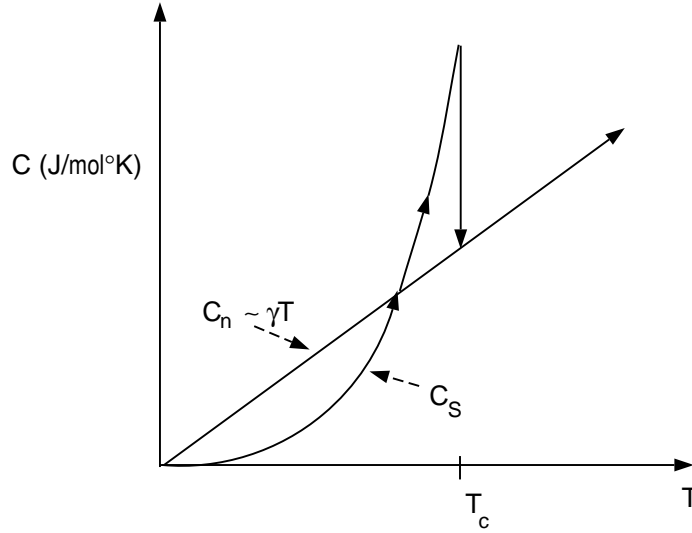


Figure 1: *The specific heat of a superconductor C_S and normal metal C_n . Below the transition, the superconductor specific heat shows activated behavior, as if there is a minimum energy for thermal excitations.*

the activated nature of C for $T < T_c$

$$C_s \sim e^{-\beta\Delta} \quad (1)$$

gives us a clue to the nature of the superconducting state. It is as if excitations require a minimum energy Δ .

1.2 Meissner Effect

There is another, much more fundamental characteristic which distinguishes the superconductor from a normal, but ideal, conductor. The superconductor expels magnetic flux, ie., $\mathbf{B} = 0$

within the bulk of a superconductor. This is fundamentally different than an ideal conductor, for which $\dot{\mathbf{B}} = 0$ since for any closed path

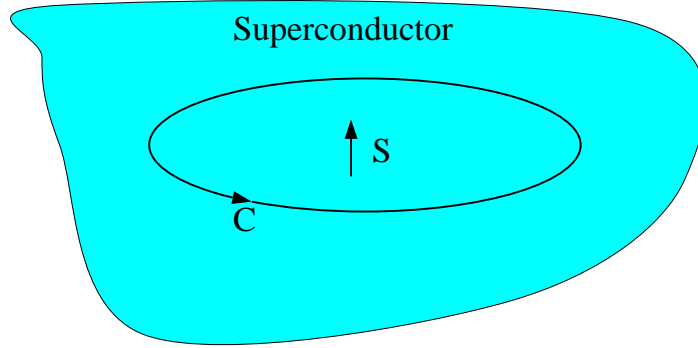


Figure 2: A closed path and the surface it contains within a superconductor.

$$0 = IR = V = \oint \mathcal{E} \cdot d\mathbf{l} = \int_S \nabla \times \mathcal{E} \cdot d\mathbf{S} = -\frac{1}{c} \int_S \frac{\partial \mathbf{B}}{\partial t} \cdot d\mathbf{S}, \quad (2)$$

or, since S and C are arbitrary

$$0 = -\frac{1}{c} \dot{\mathbf{B}} \cdot \mathbf{S} \Rightarrow \dot{\mathbf{B}} = 0 \quad (3)$$

Thus, for an ideal conductor, it matters if it is field cooled or zero field cooled. Where as for a superconductor, regardless of the external field and its history, if $T < T_c$, then $B = 0$ inside the bulk. This effect, which uniquely distinguishes an ideal conductor from a superconductor, is called the *Meissner effect*.

Ideal Conductor

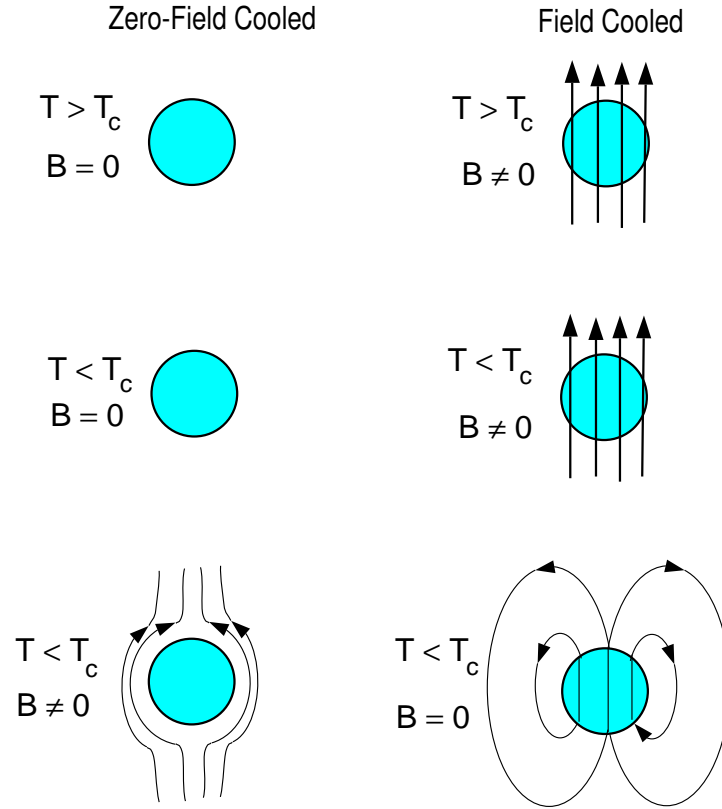


Figure 3: For an ideal conductor, flux penetration in the ground state depends on whether the sample was cooled in a field through the transition.

For this reason a superconductor is an ideal diamagnet. I.e.

$$\mathbf{B} = \mu\mathbf{H} = 0 \Rightarrow \mu = 0 \quad \mathbf{M} = \chi\mathbf{H} = \frac{\mu - 1}{4\pi}\mathbf{H} \quad (4)$$

$$\chi_{SC} = -\frac{1}{4\pi} \quad (5)$$

I.e., the measured χ , Fig. 4, in a superconducting metal is very large and negative (diamagnetic). This can also be interpreted

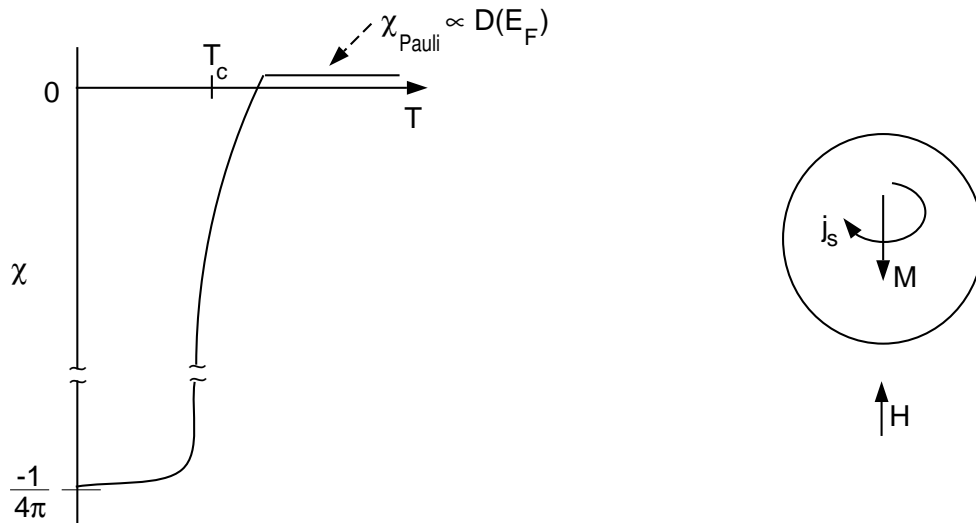


Figure 4: *LEFT: A sketch of the magnetic susceptibility versus temperature of a superconductor. RIGHT: Surface currents on a superconductor are induced to expel the external flux. The diamagnetic response of a superconductor is orders of magnitude larger than the Pauli paramagnetic response of the normal metal at $T > T_C$*

as the presence of persistent surface currents which maintain a magnetization of

$$\mathbf{M} = -\frac{1}{4\pi}H_{\text{ext}} \quad (6)$$

in the interior of the superconductor in a direction opposite to the applied field. The energy associated with this currents increases with H_{ext} . At some point it is then more favorable (ie., a lower free energy is obtained) if the system returns to a normal metallic state and these screening currents abate. Thus there exists an upper critical field H_c

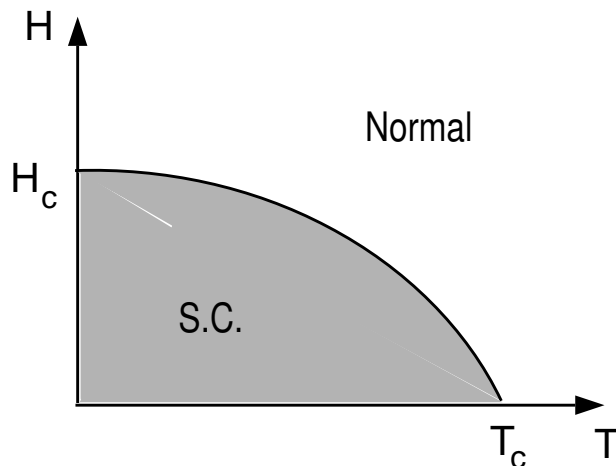


Figure 5: *Superconductivity is destroyed by either raising the temperature or by applying a magnetic field.*

2 The London Equations

London and London derived a phenomenological theory of superconductivity which correctly describes the Meissner effect. They assumed that the electrons move in a frictionless state, so that

$$m\dot{\mathbf{v}} = -e\mathcal{E} \quad (7)$$

or, since $\frac{\partial \mathbf{j}}{\partial t} = -en_s\dot{\mathbf{v}}$,

$$\frac{\partial \mathbf{j}_s}{\partial t} = \frac{e^2 n_s}{m} \mathcal{E} \quad (\text{First London Eqn.}) \quad (8)$$

Then, using the Maxwell equation

$$\nabla \times \mathcal{E} = -\frac{1}{c} \frac{\partial \mathbf{B}}{\partial t} \Rightarrow \frac{m}{n_s e^2} \nabla \times \frac{\partial \mathbf{j}_s}{\partial t} + \frac{1}{c} \frac{\partial \mathbf{B}}{\partial t} = 0 \quad (9)$$

or

$$\frac{\partial}{\partial t} \left(\frac{m}{n_s e^2} \nabla \times \mathbf{j}_s + \frac{1}{c} \mathbf{B} \right) = 0 \quad (10)$$

This described the behavior of an ideal conductor (for which $\rho = 0$), but not the Meissner effect. To describe this, the constant of integration must be chosen to be zero. Then

$$\nabla \times \mathbf{j}_s = -\frac{n_s e^2}{m c} \mathbf{B} \quad (\text{Second London Eqn.}) \quad (11)$$

or defining $\lambda_L = \frac{m}{n_s e^2}$, the London Equations become

$$\frac{\mathbf{B}}{c} = -\lambda_L \nabla \times \mathbf{j}_s \quad \mathcal{E} = \lambda_L \frac{\partial \mathbf{j}_s}{\partial t} \quad (12)$$

If we now apply the Maxwell equation $\nabla \times \mathbf{H} = \frac{4\pi}{c} \mathbf{j} \Rightarrow \nabla \times \mathbf{B} = \frac{4\pi}{c} \mu \mathbf{j}$ then we get

$$\nabla \times (\nabla \times \mathbf{B}) = \frac{4\pi}{c} \mu \nabla \times \mathbf{j} = -\frac{4\pi \mu}{c^2 \lambda_L} \mathbf{B} \quad (13)$$

and

$$\nabla \times (\nabla \times \mathbf{j}) = -\frac{1}{\lambda_L c} \nabla \times \mathbf{B} = -\frac{4\pi \mu}{c^2 \lambda_L} \mathbf{j} \quad (14)$$

or since $\nabla \cdot \mathbf{B} = 0$, $\nabla \cdot \mathbf{j} = \frac{1}{c} \frac{\partial \rho}{\partial t} = 0$ and $\nabla \times (\nabla \times \mathbf{a}) = \nabla(\nabla \cdot \mathbf{a}) - \nabla^2 \mathbf{a}$ we get

$$\nabla^2 \mathbf{B} - \frac{4\pi\mu}{c^2\lambda_L} \mathbf{B} = 0 \quad \nabla^2 \mathbf{j} - \frac{4\pi\mu}{c^2\lambda_L} \mathbf{j} = 0 \quad (15)$$

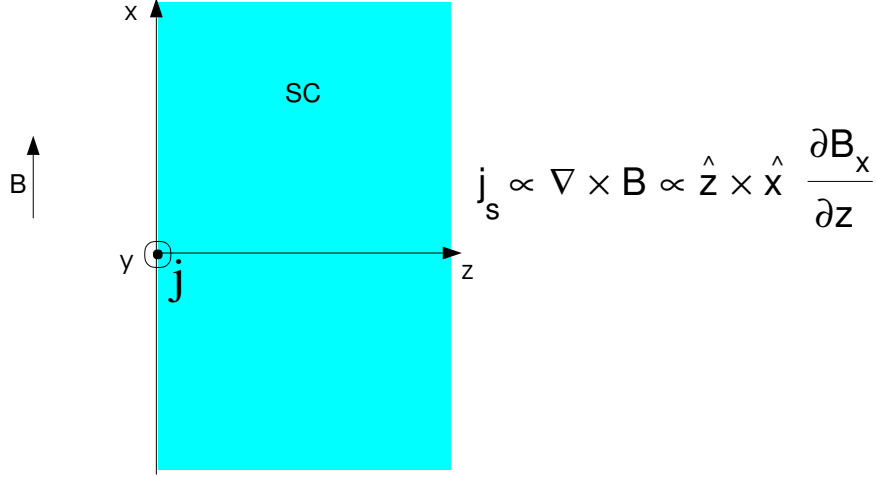


Figure 6: A superconducting slab in an external field. The field penetrates into the slab a distance $\Lambda_L = \sqrt{\frac{mc^2}{4\pi ne^2\mu}}$.

Now consider a the superconductor in an external field shown in Fig. 6. The field is only in the x-direction, and can vary in space only in the z-direction, then since $\nabla \times \mathbf{B} = \frac{4\pi}{c}\mu\mathbf{j}$, the current is in the y-direction, so

$$\frac{\partial^2 \mathbf{B}_x}{\partial z^2} - \frac{4\pi\mu}{c^2\lambda_L} \mathbf{B}_x = 0 \quad \frac{\partial^2 \mathbf{j}_{sy}}{\partial z^2} - \frac{4\pi\mu}{c^2\lambda_L} \mathbf{j}_{sy} = 0 \quad (16)$$

with the solutions

$$\mathbf{B}_x = \mathbf{B}_x^0 e^{-\frac{z}{\Lambda_L}} \quad \mathbf{j}_{sy} = \mathbf{j}_{sy} e^{-\frac{z}{\Lambda_L}} \quad (17)$$

$\Lambda_L = \sqrt{\frac{c^2\lambda_L}{4\pi\mu}} = \sqrt{\frac{mc^2}{4\pi ne^2\mu}}$ is the penetration depth.

3 Cooper Pairing

The superconducting state is fundamentally different than any possible normal metallic state (ie a perfect metal at $T = 0$). Thus, the transition from the normal metal state to the superconducting state must be a phase transition. A phase transition is accompanied by an instability of the normal state. Cooper first quantified this instability as due to a small attractive(!?) interaction between two electrons above the Fermi surface.

3.1 The Retarded Pairing Potential

The attraction comes from the exchange of phonons. The lat-

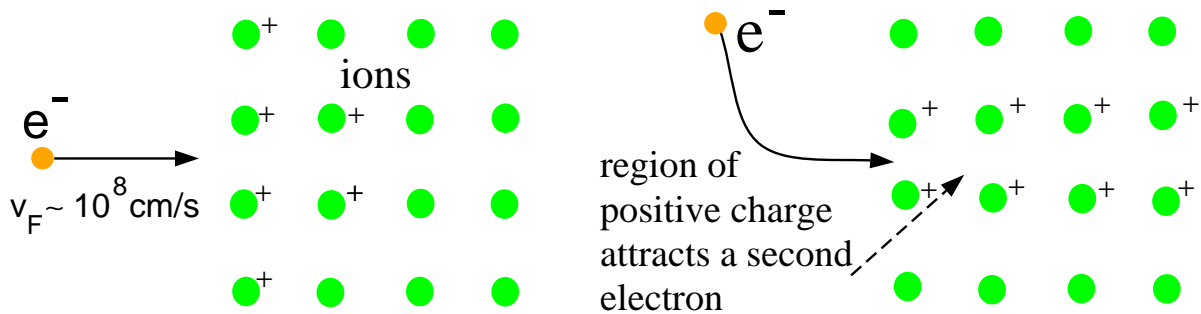


Figure 7: *Origin of the retarded attractive potential. Electrons at the Fermi surface travel with a high velocity v_F . As they pass through the lattice (left), the positive ions respond slowly. By the time they have reached their maximum excursion, the first electron is far away, leaving behind a region of positive charge which attracts a second electron.*

tice deforms slowly in the time scale of the electron. It reaches its maximum deformation at a time $\tau \sim \frac{2\pi}{\omega_D} \sim 10^{-13}\text{s}$ after the electron has passed. In this time the first electron has traveled $\sim v_F\tau \sim 10^8\frac{\text{cm}}{\text{s}} \cdot 10^{-13}\text{s} \sim 1000 \text{ \AA}$. The positive charge of the lattice deformation can then attract another electron without feeling the Coulomb repulsion of the first electron. Due to retardation, the electron-electron Coulomb repulsion may be neglected!

The net effect of the phonons is then to create an attractive interaction which tends to pair time-reversed quasiparticle states. They form an antisymmetric spin singlet so that the

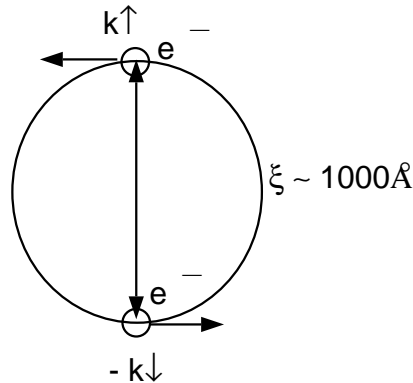


Figure 8: To take full advantage of the attractive potential illustrated in Fig. 7, the spatial part of the electronic pair wave function is symmetric and hence nodeless. To obey the Pauli principle, the spin part must then be antisymmetric or a singlet.

spatial part of the wave function can be symmetric and nodeless

and so take advantage of the attractive interaction. Furthermore they tend to pair in a zero center of mass (cm) state so that the two electrons can chase each other around the lattice.

3.2 Scattering of Cooper Pairs

This latter point may be quantified a bit better by considering two electrons above a filled Fermi sphere. These two electrons are attracted by the exchange of phonons. However, the maximum energy which may be exchanged in this way is $\sim \hbar\omega_D$. Thus the scattering in phase space is restricted to a narrow shell of energy width $\hbar\omega_D$. Furthermore, the momentum in

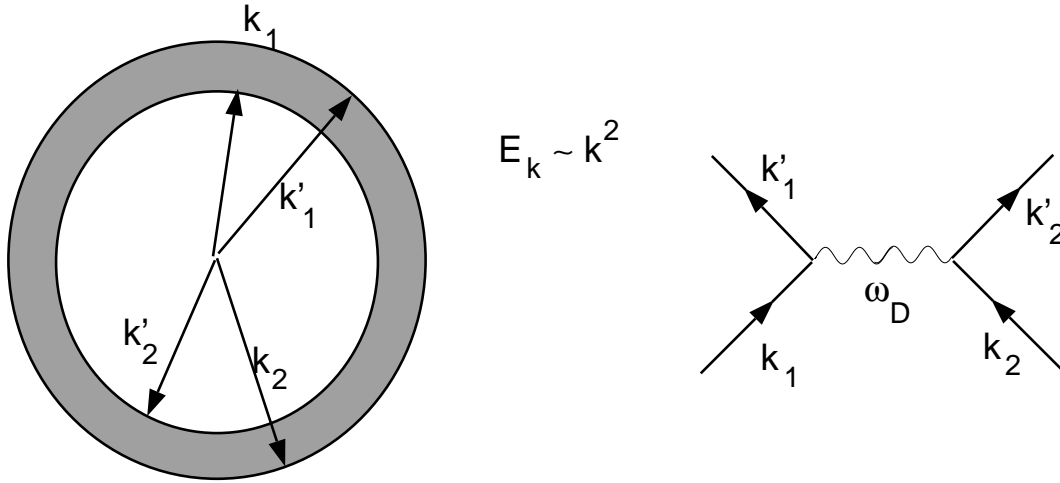


Figure 9: *Pair states scattered by the exchange of phonons are restricted to a narrow scattering shell of width $\hbar\omega_D$ around the Fermi surface.*

this scattering process is also conserved

$$\mathbf{k}_1 + \mathbf{k}_2 = \mathbf{k}'_1 + \mathbf{k}'_2 = \mathbf{K} \quad (18)$$

Thus the scattering of \mathbf{k}_1 and \mathbf{k}_2 into \mathbf{k}'_1 and \mathbf{k}'_2 is restricted to the overlap of the two scattering shells. Clearly this is negligible unless $\mathbf{K} \approx 0$. Thus the interaction is strongest (most likely) if $\mathbf{k}_1 = -\mathbf{k}_2$ and $\sigma_1 = -\sigma_2$; ie., pairing is primarily between time-reversed eigenstates.

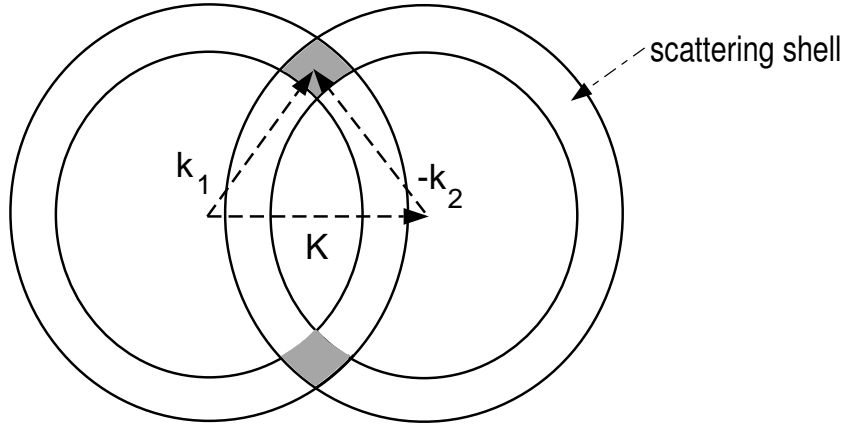


Figure 10: *If the pair has a finite center of mass momentum, so that $\mathbf{k}_1 + \mathbf{k}_2 = \mathbf{K}$, then there are few states which it can scatter into through the exchange of a phonon.*

3.3 The Cooper Instability of the Fermi Sea

Now consider these two electrons above the Fermi surface. They will obey the Schrodinger equation.

$$-\frac{\hbar^2}{2m}(\nabla_1^2 + \nabla_2^2)\psi(\mathbf{r}_1\mathbf{r}_2) + V(\mathbf{r}_1\mathbf{r}_2)\psi(\mathbf{r}_1\mathbf{r}_2) = (\epsilon + 2E_F)\psi(\mathbf{r}_1\mathbf{r}_2) \quad (19)$$

If $V = 0$, then $\epsilon = 0$, and

$$\psi_{V=0} = \frac{1}{L^{3/2}}e^{i\mathbf{k}_1\cdot\mathbf{r}_1} \frac{1}{L^{3/2}}e^{i\mathbf{k}_2\cdot\mathbf{r}_2} = \frac{1}{L^3}e^{i\mathbf{k}(\mathbf{r}_1-\mathbf{r}_2)}, \quad (20)$$

where we assume that $\mathbf{k}_1 = -\mathbf{k}_2 = \mathbf{k}$. For small V , we will perturb around the $V = 0$ state, so that

$$\psi(\mathbf{r}_1\mathbf{r}_2) = \frac{1}{L^3} \sum_{\mathbf{k}} g(\mathbf{k})e^{i\mathbf{k}\cdot(\mathbf{r}_1-\mathbf{r}_2)} \quad (21)$$

The sum must be restricted so that

$$E_F < \frac{\hbar^2\mathbf{k}^2}{2m} < E_F + \hbar\omega_D \quad (22)$$

this may be imposed by $g(\mathbf{k})$, since $|g(\mathbf{k})|^2$ is the probability of finding an electron in a state \mathbf{k} and the other in $-\mathbf{k}$. Thus we take

$$g(\mathbf{k}) = 0 \quad \text{for} \quad \begin{cases} \mathbf{k} < \mathbf{k}_F \\ \mathbf{k} > \frac{\sqrt{2m(E_F+\hbar\omega_D)}}{\hbar} \end{cases} \quad (23)$$

The Schroedinger equations may be converted to a k-space equation by multiplying it by

$$\frac{1}{L^3} \int d^3\mathbf{r} e^{-i\mathbf{k}' \cdot \mathbf{r}} \Rightarrow \text{S.E.} \quad (24)$$

so that

$$\frac{\hbar^2 k^2}{m} g(\mathbf{k}) + \frac{1}{L^3} \sum_{\mathbf{k}'} g(\mathbf{k}') V_{\mathbf{k}\mathbf{k}'} = (\epsilon + 2E_F) g(\mathbf{k}) \quad (25)$$

where

$$V_{\mathbf{k}\mathbf{k}'} = \int V(\mathbf{r}) e^{-i(\mathbf{k} - \mathbf{k}') \cdot \mathbf{r}} d^3\mathbf{r} \quad (26)$$

now describes the scattering from $(\mathbf{k}, -\mathbf{k})$ to $(\mathbf{k}', -\mathbf{k}')$. It is usually approximated as a constant for all \mathbf{k} and \mathbf{k}' which obey the Pauli-principle and scattering shell restrictions

$$V_{\mathbf{k}\mathbf{k}'} = \begin{cases} -V_0 & E_F < \frac{\hbar^2 \mathbf{k}^2}{2m}, \frac{\hbar^2 \mathbf{k}'^2}{2m} < E_F + \hbar\omega_D \\ 0 & \text{otherwise} \end{cases} . \quad (27)$$

so

$$\left(-\frac{\hbar^2 \mathbf{k}^2}{m} + \epsilon + 2E_F \right) g(\mathbf{k}) = -\frac{V_0}{L^3} \sum_{\mathbf{k}'} g(\mathbf{k}') \equiv -A \quad (28)$$

or

$$g(\mathbf{k}) = \frac{-A}{-\frac{\hbar^2 \mathbf{k}^2}{m} + \epsilon + 2E_F} \quad (\text{i.e. for } E_F < \frac{\hbar^2 \mathbf{k}^2}{2m} < E_F + \hbar\omega_D) \quad (29)$$

Summing over \mathbf{k}

$$\frac{V_0}{L^3} \sum_{\mathbf{k}} \frac{A}{\frac{\hbar^2 \mathbf{k}^2}{m} - \epsilon - 2E_F} = +A \quad (30)$$

or

$$1 = \frac{V_0}{L^3} \sum_{\mathbf{k}} \frac{1}{\frac{\hbar^2 \mathbf{k}^2}{m} - \epsilon - 2E_F} \quad (31)$$

This may be converted to a density of states integral on $E = \frac{\hbar^2 \mathbf{k}^2}{2m}$

$$1 = V_0 \int_{E_F}^{E_F + \hbar\omega_D} Z(E_F) \frac{dE}{2E - \epsilon - 2E_F} \quad (32)$$

$$1 = \frac{1}{2} V_0 Z(E_F) \ln \left(\frac{\epsilon - 2\hbar\omega_D}{\epsilon} \right) \quad (33)$$

$$\epsilon = \frac{2\hbar\omega_D}{1 - e^{2/(V_0 Z(E_F))}} \simeq -2\hbar\omega_D e^{-2/(V_0 Z(E_F))} < 0, \quad \text{as } \frac{V_0}{E_F} \rightarrow 0 \quad (34)$$

4 The BCS Ground State

In the preceding section, we saw that the weak phonon-mediated attractive interaction was sufficient to destabilize the Fermi sea, and promote the formation of a Cooper pair ($\mathbf{k} \uparrow, -\mathbf{k} \downarrow$). The scattering

$$(\mathbf{k} \uparrow, -\mathbf{k} \downarrow) \rightarrow (\mathbf{k}' \uparrow, -\mathbf{k}' \downarrow) \quad (35)$$

yields an energy V_0 if \mathbf{k} and \mathbf{k}' are in the scattering shell $E_F < E_{\mathbf{k}}, E_{\mathbf{k}'} < E_F + \hbar\omega_D$. Many electrons can participate in this process and many Cooper pairs are formed, yielding a new state (phase) of the system. The energy of this new state is *not* just $\frac{N}{2}\epsilon$ less than that of the old state, since the Fermi surface is renormalized by the formation of each Cooper pair.

4.1 The Energy of the BCS Ground State

Of course, to study the thermodynamics of this new phase, it is necessary to determine its energy. It will have both kinetic and potential contributions. Since pairing only occurs for electrons *above* the Fermi surface, the kinetic energy actually increases: if w_k is the probability that a pair state $(\mathbf{k} \uparrow, -\mathbf{k} \downarrow)$ is occupied then

$$E_{\text{kin}} = 2 \sum_{\mathbf{k}} w_k \xi_k, \quad \xi_k = \frac{\hbar^2 \mathbf{k}^2}{2m} - E_F \quad (36)$$

The potential energy requires a bit more thought. It may be written in terms of annihilation and creation operators for the

pair states labeled by \mathbf{k}

$$|1\rangle_k \quad (\mathbf{k} \uparrow, -\mathbf{k} \downarrow)\text{occupied} \quad (37)$$

$$|0\rangle_k \quad (\mathbf{k} \uparrow, -\mathbf{k} \downarrow)\text{unoccupied} \quad (38)$$

or

$$|\psi_k\rangle = u_k |0\rangle_k + v_k |1\rangle_k \quad (39)$$

where $v_k^2 = w_k$ and $u_k^2 = 1 - w_k$. Then the BCS state, which is a collection of these pairs, may be written as

$$|\phi_{BCS}\rangle \simeq \prod_k \{u_k |0\rangle_k + v_k |1\rangle_k\} . \quad (40)$$

We will assume that $u_k, v_k \in \mathfrak{R}$. Physically this amounts to taking the phase of the order parameter to be zero (or π), so that it is real. However the validity of this assumption can only be verified for a more microscopically based theory.

By the Pauli principle, the state $(\mathbf{k} \uparrow, -\mathbf{k} \downarrow)$ can be, at most, singly occupied, thus a ($s = \frac{1}{2}$) Pauli representation is possible

$$|1\rangle_k = \begin{pmatrix} 1 \\ 0 \end{pmatrix}_k \quad |0\rangle_k = \begin{pmatrix} 0 \\ 1 \end{pmatrix}_k \quad (41)$$

Where σ_k^+ and σ_k^- , describe the creation and annihilation of the

state ($\mathbf{k} \uparrow, -\mathbf{k} \downarrow$)

$$\sigma_k^+ = \frac{1}{2}(\sigma_k^1 + i\sigma_k^2) = \begin{pmatrix} 0 & 1 \\ 0 & 0 \end{pmatrix} \quad (42)$$

$$\sigma_k^- = \frac{1}{2}(\sigma_k^1 - i\sigma_k^2) = \begin{pmatrix} 0 & 0 \\ 1 & 0 \end{pmatrix} \quad (43)$$

Of course $\sigma_k^+ \begin{pmatrix} 0 \\ 1 \end{pmatrix}_k = \begin{pmatrix} 1 \\ 0 \end{pmatrix}_k$

$$\sigma_k^+ |1\rangle_k = 0 \quad \sigma_k^+ |0\rangle_k = |1\rangle_k \quad (44)$$

$$\sigma_k^- |1\rangle_k = |0\rangle_k \quad \sigma_k^- |0\rangle_k = 0 \quad (45)$$

The process ($\mathbf{k} \uparrow, -\mathbf{k} \downarrow$) \rightarrow ($\mathbf{k}' \uparrow, -\mathbf{k}' \downarrow$), if allowed, is associated with an energy reduction V_0 . In our Pauli matrix representation this process is represented by operators $\sigma_{\mathbf{k}'}^+ \sigma_{\mathbf{k}}^-$, so

$$V = -\frac{V_0}{L^3} \sum_{\mathbf{k}\mathbf{k}'} \sigma_{\mathbf{k}'}^+ \sigma_{\mathbf{k}}^- \quad (\text{Note that this is Hermitian}) \quad (46)$$

Thus the reduction of the potential energy is given by $\langle \phi_{BCS} | V | \phi_{BCS} \rangle$

$$\langle \phi_{BCS} | V | \phi_{BCS} \rangle = -\frac{V_0}{L^3} \left\{ \prod_p (u_p \langle 0 | + v_p \langle 1 |) \sum_{\mathbf{k}\mathbf{k}'} \sigma_{\mathbf{k}}^+ \sigma_{\mathbf{k}'}^- \prod_{p'} (u_{p'} |0\rangle_{p'} + v_{p'} |1\rangle_{p'}) \right\} \quad (47)$$

Then as ${}_k \langle 1|1\rangle_{k'} = \delta_{kk'}$, ${}_k \langle 0|0\rangle_{k'} = \delta_{kk'}$ and ${}_k \langle 0|1\rangle_{k'} = 0$

$$\langle \phi_{BCS} | V | \phi_{BCS} \rangle = -\frac{V_0}{L^3} \sum_{kk'} v_k u_{k'} u_k v_{k'} \quad (48)$$

Thus, the total energy (kinetic plus potential) of the system of Cooper pairs is

$$W_{BCS} = 2 \sum_k v_k^2 \xi_k - \frac{V_0}{L^3} \sum_{kk'} v_k u_{k'} u_k v_{k'} \quad (49)$$

As yet v_k and u_k are unknown. They may be treated as variational parameters. Since $w_k = v_k^2$ and $1 - w_k = u_k^2$, we may impose this constraint by choosing

$$v_k = \cos \theta_k, \quad u_k = \sin \theta_k \quad (50)$$

At $T = 0$, we require W_{BCS} to be a minimum.

$$\begin{aligned} W_{BCS} &= \sum_k 2\xi_k \cos^2 \theta_k - \frac{V_0}{L^3} \sum_{kk'} \cos \theta_k \sin \theta_{k'} \cos \theta_{k'} \sin \theta_k \\ &= \sum_k 2\xi_k \cos^2 \theta_k - \frac{V_0}{L^3} \sum_{kk'} \frac{1}{4} \sin 2\theta_k \sin 2\theta_{k'} \quad (51) \end{aligned}$$

$$\frac{\partial W_{BCS}}{\partial \theta_k} = 0 = -4\xi_k \cos \theta_k \sin \theta_k - \frac{V_0}{L^3} \sum_{k'} \cos 2\theta_k \sin 2\theta_{k'} \quad (52)$$

$$\xi_k \tan 2\theta_k = -\frac{1}{2} \frac{V_0}{L^3} \sum_{k'} \sin 2\theta_{k'} \quad (53)$$

Conventionally, one introduces the parameters $E_k = \sqrt{\xi_k^2 + \Delta^2}$, $\Delta = \frac{V_0}{L^3} \sum_k u_k v_k = \frac{V_0}{L^3} \sum_k \cos \theta_k \sin \theta_k$. Then we get

$$\xi_k \tan 2\theta_k = -\Delta \Rightarrow 2u_k v_k = \sin 2\theta_k = \frac{\Delta}{E_k} \quad (54)$$

$$\cos 2\theta_k = \frac{-\xi_k}{E_k} = \cos^2 \theta_k - \sin^2 \theta_k = v_k^2 - u_k^2 = 2v_k^2 - 1 \quad (55)$$

$$w_k = v_k^2 = \frac{1}{2} \left(1 - \frac{-\xi_k}{E_k} \right) = \frac{1}{2} \left(1 - \frac{\xi_k}{\sqrt{\xi_k^2 + \Delta^2}} \right) \quad (56)$$

If we now make these substitutions $\left(2u_k v_k = \frac{\Delta}{E_k}, v_k^2 = \frac{1}{2} \left(1 - \frac{\xi_k}{E_k} \right) \right)$

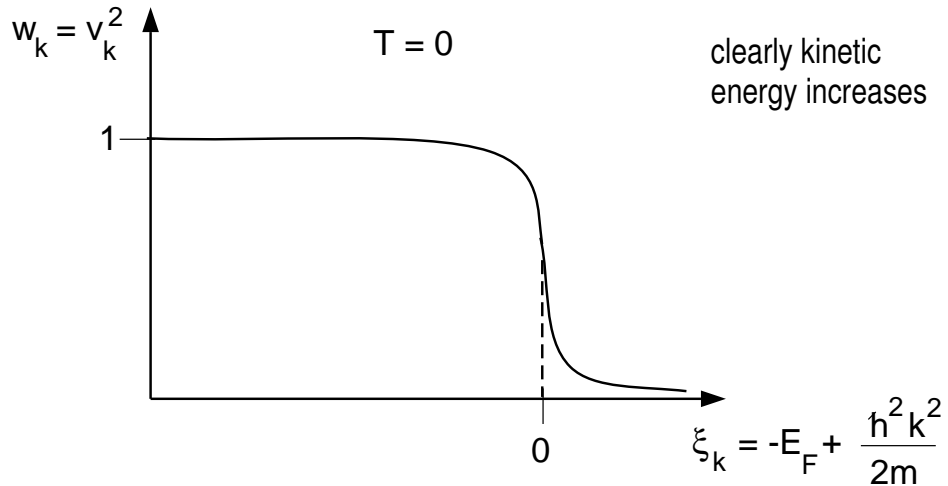


Figure 11: *Sketch of the ground state pair distribution function.*

into W_{BCS} , then we get

$$W_{BCS} = \sum_k \xi_k \left(1 - \frac{\xi_k}{E_k} \right) - \frac{L^3}{V_0} \Delta^2. \quad (57)$$

Compare this to the normal state energy, again measured relative to E_F

$$W_n = \sum_{k < k_F} 2\xi_k \quad (58)$$

or

$$\frac{W_{BCS} - W_n}{L^3} = -\frac{1}{L^3} \sum_k \xi_k \left(1 + \frac{\xi_k}{E_k} \right) - \frac{\Delta^2}{V_0} \quad (59)$$

$$\approx -\frac{1}{2} Z(E_F) \Delta^2 < 0. \quad (60)$$

So the formation of superconductivity reduces the ground state energy. This can also be interpreted as $\Delta Z(E_F)$ electrons pairs per and volume condensed into a state Δ below E_F . The average energy gain per electron is $\frac{\Delta}{2}$.

4.2 The BCS Gap

The gap parameter Δ is fundamental to the BCS theory. It tells us both the energy gain of the BCS state, and about its excitations. Thus Δ is usually what is measured by experiments. To

see this consider

$$W_{BCS} = \sum_k 2\xi_k \frac{1}{2} \left(1 - \frac{\xi_k}{E_k} \right) - \frac{L^3 \Delta^2}{V_0} \quad (61)$$

↓ Lots of algebra (See I&L)

$$W_{BCS} = - \sum_k 2E_k v_k^4 \quad (62)$$

Now recall that the probability that the Cooper state ($\mathbf{k} \uparrow, \mathbf{k} \downarrow$) was occupied, is given by $w_k = v_k^2$. Thus the first pair breaking excitation takes $v_{k'}^2 = 1$ to $v_{k'}^2 = 0$, for a change in energy

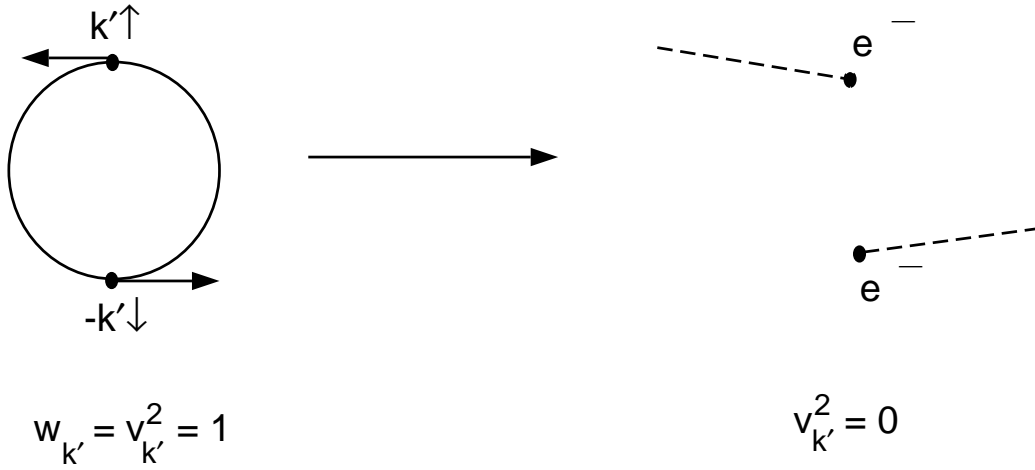


Figure 12: *Breaking a pair requires an energy $2\sqrt{\xi_{\mathbf{k}}^2 + \Delta^2} \geq 2\Delta$*

$$\Delta E = - \sum_{k \neq k'} 2v_k^4 E_k + \sum_k 2v_k^4 E_k = 2E_{k'} = 2\sqrt{\xi_{k'}^2 + \Delta^2} \quad (63)$$

Then since $\xi_{k'} = \frac{\hbar^2 k'^2}{2m} - E_F$, the smallest such excitation is just

$$\Delta E_{min} = 2\Delta \quad (64)$$

This is the minimum energy required to break a pair, or create an excitation in the BCS ground state. It is what is measured by the specific heat $C \sim e^{-\beta 2\Delta}$ for $T < T_c$.

Now consider some experiment which adds a *single* electron, or perhaps a few unpaired electrons, to a superconductor (ie tunneling). This additional electron cannot find a partner for

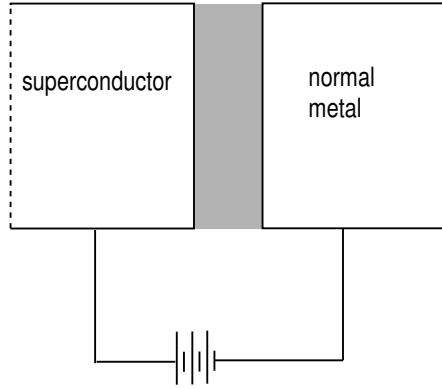


Figure 13:

pairing. Thus it must enter one of the excited states discussed above. Since it is a single electron, its energy will be

$$E_k = \sqrt{\xi_k^2 + \Delta^2} \quad (65)$$

For $\xi_k^2 \gg \Delta$, $E_k = \xi_k = \frac{\hbar^2 k'^2}{2m} - E_F$, which is just the energy of a normal metal state. Thus for energies well above the gap, the normal metal continuum is recovered for unpaired electrons.

To calculate the density of unpaired electron states, recall that the density of states was determined by counting k -states. These are unaffected by any phase transition. Thus it must be that the number of states in d^3k is equal.

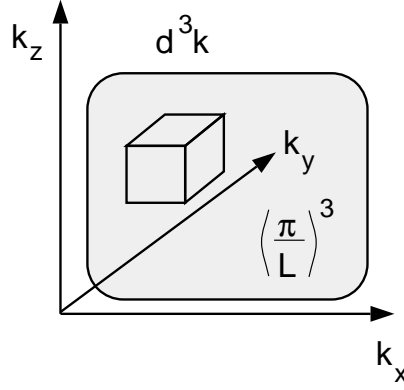


Figure 14: *The number of k -states within a volume d^3k of k -space is unaffected by any phase transition.*

$$D_s(E_k)dE_k = D_n(\xi_k)d\xi_k \quad (66)$$

In the vicinity of $\Delta \sim \xi_k$, $D_n(\xi_k) \approx D_n(E_F)$ since $|\Delta| \ll E_F$ (we shall see that $\Delta \leq 2w_D$). Thus for $\xi_k \sim \Delta$

$$\frac{D_s(E_k)}{D_n(E_F)} = \frac{d\xi_x}{dE_k} = \frac{d}{dE_k} \sqrt{E_k^2 - \Delta^2} = \frac{E_k}{\sqrt{E_k^2 - \Delta^2}} \quad E_k > \Delta \quad (67)$$

Given the experimental and theoretical importance of Δ , it

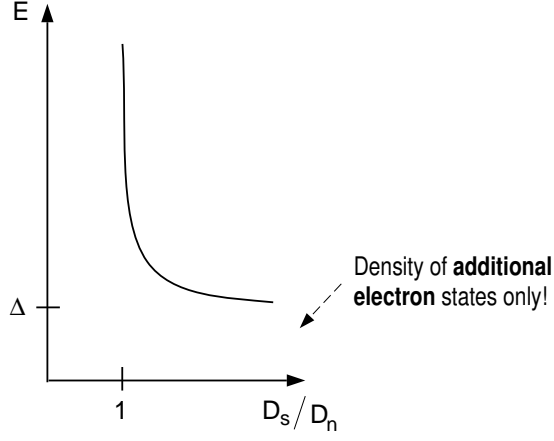


Figure 15:

should be calculated.

$$\Delta = \frac{V_0}{L^3} \sum_k \sin \theta_k \cos \theta_k = \frac{V_0}{L^3} \sum_k u_k v_k = \frac{V_0}{L^3} \sum_k \frac{\Delta}{2E_k} \quad (68)$$

$$\Delta = \frac{1}{2} \frac{V_0}{L^3} \sum_k \frac{\Delta}{\sqrt{\xi_k^2 + \Delta^2}} \quad (69)$$

Convert this to sum over energy states (at $T = 0$ all states with $\xi < 0$ are occupied since $\xi_k = \frac{\hbar^2 \mathbf{k}^2}{2m} - E_F$).

$$\Delta = \frac{V_0}{2} \Delta \int_{-\hbar\omega_D}^{\hbar\omega_D} \frac{Z(E_F + \xi) d\xi}{\sqrt{\xi^2 + \Delta^2}} \quad (70)$$

$$\frac{1}{V_0 Z(E_F)} = \int_0^{\hbar\omega_D} \frac{d\xi}{\sqrt{\xi^2 + \Delta^2}} \quad (71)$$

$$\frac{1}{V_0 Z(E_F)} = \sinh^{-1} \left(\frac{\hbar\omega_D}{\Delta} \right) \quad (72)$$

For small Δ ,

$$\frac{\hbar\omega_D}{\Delta} \sim e^{\frac{1}{V_0 Z(E_F)}} \quad (73)$$

$$\Delta \simeq \hbar\omega_D e^{-\frac{1}{V_0 Z(E_F)}} \quad (74)$$

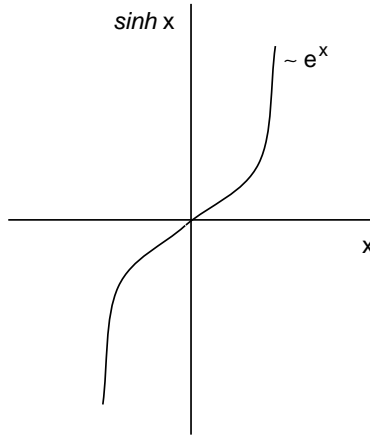


Figure 16:

5 Consequences of BCS and Experiment

5.1 Specific Heat

As mentioned before, the gap Δ is fundamental to experiment. The simplest excitation which can be induced in a superconductor has energy 2Δ . Thus

$$\Delta E \sim 2\Delta e^{-\beta 2\Delta} \quad T \ll T_c \quad (75)$$

$$C \sim \frac{\partial \Delta E}{\partial \beta} \frac{\partial \beta}{\partial T} \sim \frac{\Delta^2}{T^2} e^{-\beta 2\Delta} \quad (76)$$

5.2 Microwave Absorption and Reflection

Another direct measurement of the gap is reflectivity/absorption. A phonon impacting a superconductor can either be reflected or absorbed. Unless $\hbar\omega > 2\Delta$, the phonon cannot create an excitation and is reflected. Only if $\hbar\omega > 2\Delta$ is there absorption. Consider a small cavity within a superconductor. The cavity has a small hole which allows microwave radiation to enter the cavity. If $\hbar\omega < 2\Delta$ and if $B < B_c$, then the microwave in-

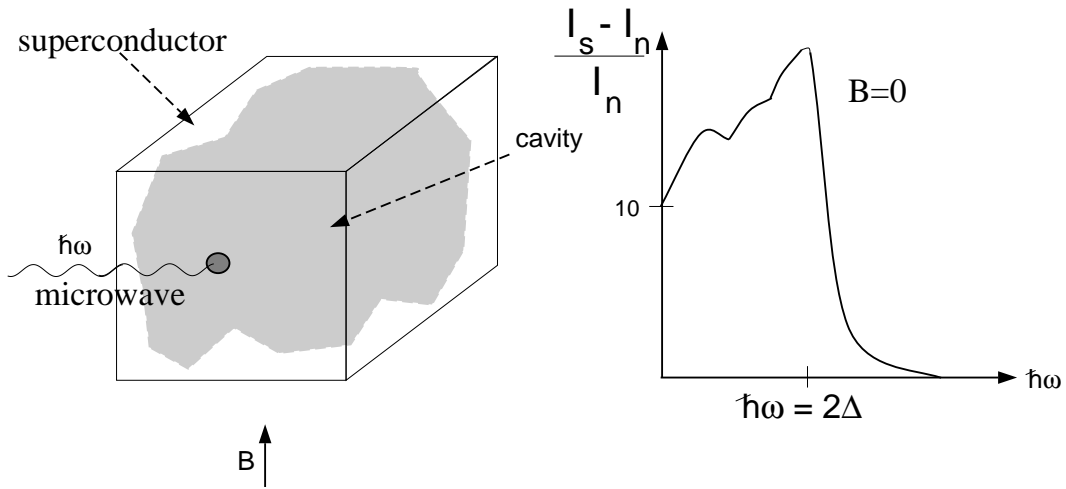


Figure 17: If $B > B_c$ or $\hbar\omega > 2\Delta$, then absorption reduces the intensity to the normal-state value $I = I_n$. For $B = 0$ the microwave intensity within the cavity is large so long as $\hbar\omega < 2\Delta$

tensity is high $I = I_s$. On the other hand, if $\hbar\omega > 2\Delta$, or $B > B_c$, then the intensity falls in the cavity $I = I_n$ due to absorption by the walls.

Note that this also allows us to measure Δ as a function of T . At $T = T_c$, $\Delta = 0$, since thermal excitations reduce the number of Cooper pairs and increase the number of unpaired electrons, which obey Fermi-statistics. The size of (Eqn. 71) is

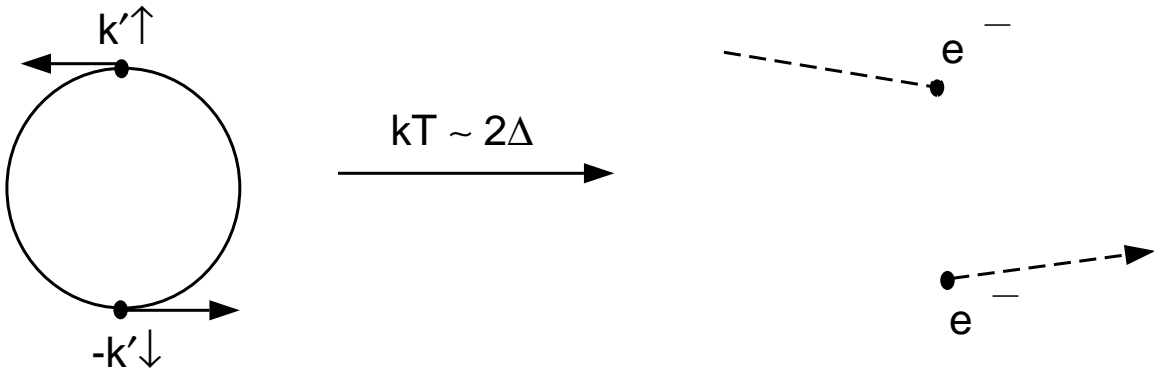


Figure 18:

only effected by the presence of a Cooper pair . The probability that an electron is unpaired is $f\left(\sqrt{\xi^2 + \Delta^2} + E_F, T\right) = \frac{1}{\exp \beta \sqrt{\xi^2 + \Delta^2} + 1}$ so, the probability that a Cooper pair exists is

$1 - 2f\left(\sqrt{\xi^2 + \Delta^2} + E_F, T\right)$. Thus for $T \neq 0$

$$\frac{1}{V_0 Z(E_F)} = \int_0^{\hbar\omega_D} \frac{d\xi}{\sqrt{\xi^2 + \Delta^2}} \left\{ 1 - 2f\left(\sqrt{\xi^2 + \Delta^2} + E_F, T\right) \right\} \quad (77)$$

Note that as $\sqrt{\xi^2 + \Delta^2} \geq 0$, when $\beta \rightarrow \infty$ we recover the $T = 0$ result.

This equation may be solved for $\Delta(T)$ and for T_c . To find T_c

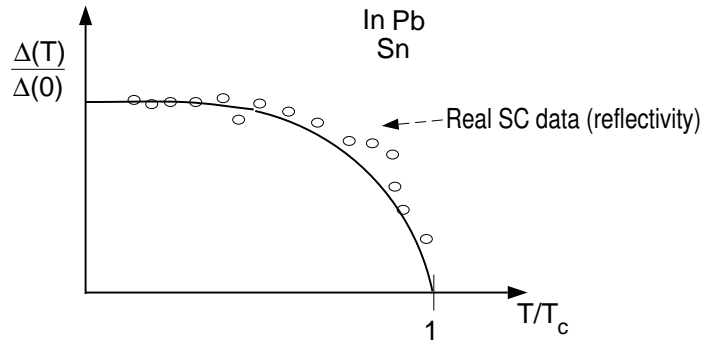


Figure 19: *The evolution of the gap (as measured by reflectivity) as a function of temperature. The BCS approximation is in reasonably good agreement with experiment.*

consider this equation as $\frac{T}{T_c} \rightarrow 1$, the first solution to the gap equation, with $\Delta = 0^+$, occurs at $T = T_c$. Here

$$\frac{1}{V_0 Z(E_F)} = \int_0^{\hbar\omega_D} \frac{d\xi}{\xi} \tanh\left(\frac{\xi}{2k_B T_c}\right) \quad (78)$$

which may be solved numerically to yield

$$1 = V_0 Z(E_F) \ln \frac{1.14\hbar\omega_D}{k_B T_c} \quad (79)$$

$$k_B T_c = 1.14 \hbar \omega_D e^{-1/\{V_0 Z(E_F)\}} \quad (80)$$

but recall that $\Delta = 2 \hbar \omega_D e^{-1/\{V_0 Z(E_F)\}}$, so

$$\frac{\Delta(0)}{k_B T_c} = \frac{2}{1.14} = 1.764 \quad (81)$$

metal	T_c °K	$Z(E_F)V_0$	$\Delta(0)/k_B T_c$
Zn	0.9	0.18	1.6
Al	1.2	0.18	1.7
Pb	7.22	0.39	2.15

Table 1: *Note that the value 2.15 for $\Delta(0)/k_B T_c$ for Pb is higher than BCS predicts. Such systems are labeled strong coupling superconductors and are better described by the Eliashberg-Migdal theory.*

5.3 The Isotope Effect

Finally, one should discuss the isotope effect. We know that $V_{kk'}$, results from phonon exchange. If we change the mass of one of the vibrating members but not its charge, then $V_0 N(E_F)$ etc are unchanged but

$$\omega_D \sim \sqrt{\frac{k}{M}} \sim M^{-\frac{1}{2}}. \quad (82)$$

Thus $T_c \sim M^{-\frac{1}{2}}$. This has been confirmed for most normal superconductors, and is considered a "smoking gun" for phonon mediated superconductivity.

6 BCS \Rightarrow Superconducting Phenomenology

Using Maxwell's equations, we may establish a relation between the critical current and the critical field necessary to destroy the superconducting state. Consider a long thick wire (with radius $r_0 \gg \Lambda_L$) and integrate the equation

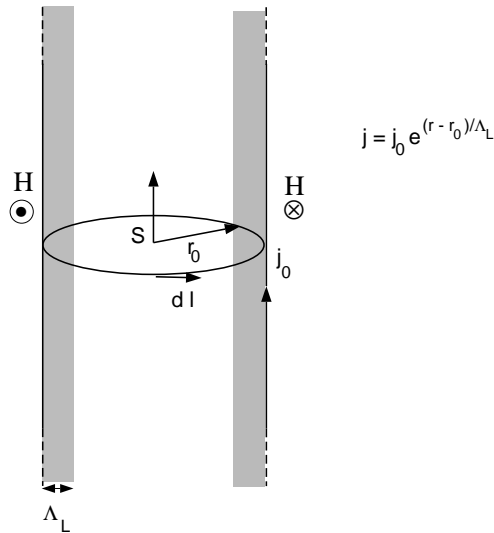


Figure 20: *Integration contour within a long thick superconducting wire perpendicular to a circulating magnetic field. The field only penetrates into the wire a distance Λ_L .*

$$\nabla \times \mathbf{H} = \frac{4\pi}{c} \mathbf{j} \quad (83)$$

along the contour shown in Fig. 20.

$$\int \nabla \times \mathbf{H} dS = \int \mathbf{H} \cdot d\mathbf{l} = \frac{4\pi}{c} \int \mathbf{j} \cdot d\mathbf{s} \quad (84)$$

$$2\pi r_0 H = \frac{4\pi}{c} 2\pi r_0 \Lambda_L j_0 \quad (85)$$

If $\mathbf{j}_0 = \mathbf{j}_c$ (\mathbf{j}_c is the critical current), then

$$H_c = \frac{4\pi}{c} \Lambda_L \mathbf{j}_c \quad (86)$$

Since both H_c and $j_c \propto \Delta$, they will share the temperature-dependence of Δ .

At $T = 0$, we could also get an expression for H_c by noting that, since the superconducting state excludes all flux,

$$\frac{1}{L^3} (W_n - W_{BCS}) = \frac{1}{8\pi} \mathbf{H}_c^2 \quad (87)$$

However, since we have earlier

$$\frac{1}{L^3} (W_n - W_{BCS}) = \frac{1}{2} N(0) \Delta^2, \quad (88)$$

we get

$$H_c = 2\Delta \sqrt{\pi N(0)} \quad (89)$$

We can use this, and the relation derived above $j_c = \frac{c}{4\pi\Lambda_L} H_c$,

to get a (properly derived) relationship for j_c .

$$j_c = \frac{c}{4\pi\Lambda_L} 2\Delta \sqrt{\pi N(0)} \quad (90)$$

However, for most metals

$$N(0) \simeq \frac{n}{E_F} \quad (91)$$

$$\Lambda_L = \sqrt{\frac{mc^2}{4\pi ne^2 \mu}} \quad (92)$$

taking $\mu = 1$

$$j_c = \frac{c}{4\pi} \sqrt{\frac{4\pi ne^2}{mc^2}} 2\Delta \sqrt{\frac{\pi n 2m}{\hbar^2 k_F^2}} = \sqrt{2} \Delta \frac{ne}{\hbar k_F} \quad (93)$$

This gives a similar result to what Ibach and Lüth get, but for a completely different reason. Their argument is similar to one originally proposed by Landau. Imagine that you have a fluid which must flow around an obstacle of mass M . From the perspective of the fluid, this is the same as an obstacle moving in it. Suppose the obstacle makes an excitation of energy ϵ and momentum \mathbf{p} in the fluid, then

$$E' = E - \epsilon \quad \mathbf{P}' = \mathbf{P} - \mathbf{p} \quad (94)$$

or from squaring the second equation and dividing by $2M$




Figure 21: A superconducting fluid which must flow around an obstacle of mass M . From the perspective of the fluid, this is the same as an obstacle, with a velocity equal and opposite the fluids, moving in it.

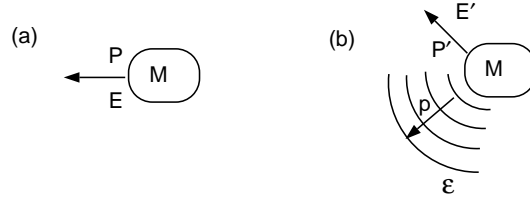


Figure 22: A large mass M moving with momentum \mathbf{P} in a superfluid (a), creates an excitation (b) of the fluid of energy ϵ and momentum \mathbf{p}

$$\frac{P'^2}{2M} - \frac{P^2}{2M} = -\frac{\mathbf{P} \cdot \mathbf{p}}{M} + \frac{\mathbf{p}^2}{2M} = E' - E = \epsilon \quad (95)$$

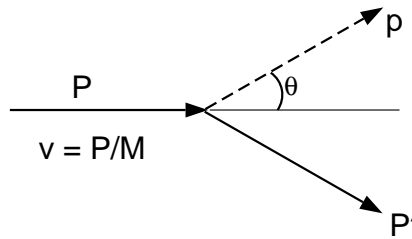


Figure 23:

$$\epsilon = \frac{pP \cos \theta}{M} - \frac{p^2}{2M} \quad (96)$$

$$\epsilon = pv \cos \theta - \frac{p^2}{2M} \quad (97)$$

If $M \rightarrow \infty$ (a defect in the tube which carries the fluid could have essentially an infinite mass) then

$$\frac{\epsilon}{p} = v \cos \theta \quad (98)$$

Then since $\cos \theta \leq 1$

$$v \geq \frac{\epsilon}{p} \quad (99)$$

Thus, if there is some minimum ϵ , then there is also a minimum velocity below which such excitations of the fluid cannot happen. For the superconductor

$$v_c = \frac{\epsilon_{min}}{p} = \frac{2\Delta}{2\hbar k_F} \quad (100)$$

Or

$$j_c = env_c = \Delta \frac{ne}{\hbar k_F} \quad (101)$$

This is the same relation as we obtained with the previous thermodynamic argument (within a factor $\sqrt{2}$). However, the former argument is more proper, since it would apply even for *gapless* superconductors, and it takes into account the fact that the S.C. state is a collective phenomena ie., a minuet, not a waltz of electric pairs.

7 Coherence of the Superconductor \Rightarrow Meissner effects

Superconductivity *is* the Meissner effect, but thus far, we have not yet shown that the BCS theory leads to the second London equation which describes flux exclusion. In this subsection, we will see that this requires an additional assumption: the rigidity of the BCS wave function.

In the BCS approximation, the superconducting wave function is taken to be composed of products of Cooper pairs. One can estimate the size of the pairs from the uncertainty principle

$$2\Delta = \delta \left(\frac{\mathbf{p}^2}{2m} \right) \sim \frac{\mathbf{p}_F}{m} \delta \mathbf{p} \Rightarrow \delta \mathbf{p} \sim 2m \frac{\Delta}{\mathbf{p}_F} \quad (102)$$

$$\xi_{cp} \sim \delta x \sim \frac{\hbar}{\delta \mathbf{p}} \sim \frac{\hbar \mathbf{p}_F}{2m\Delta} = \frac{\hbar^2 \mathbf{k}_F}{2m\Delta} = \frac{E_F}{\mathbf{k}_F \Delta} \quad (103)$$

$$\xi_{cp} \sim 10^3 - 10^4 \text{ \AA} \sim \text{size of Cooper pair wave function} \quad (104)$$

Thus in the radius of the Cooper pair, about

$$\frac{4\pi n}{3} \left(\frac{\xi_{cp}}{2} \right)^3 \sim 10^8 \quad (105)$$

other pairs have their center of mass.

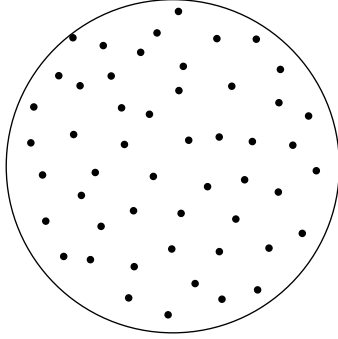


Figure 24: *Many electron pairs fall within the volume of a Cooper wavefunction. This leads to a degree of correlation between the pairs and to rigidity of the pair wavefunction.*

The pairs are thus *not* independent of each other (regardless of the BCS wave function approximation). In fact they are specifically anchored to each other; i.e., they maintain coherence over a length scale of at least ξ_{cp} .

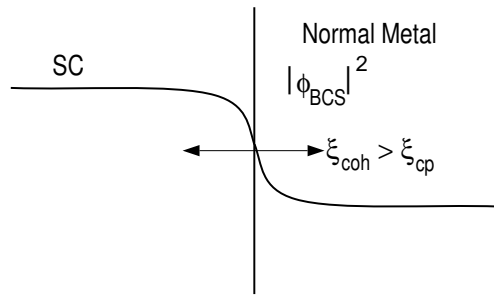


Figure 25:

In light of this coherence, lets reconsider the supercurrent

$$\mathbf{j} = -\frac{2e}{4m} \{ \psi \mathbf{p}^* \psi^* + \psi^* \mathbf{p} \psi \} \quad (106)$$

where pair mass = $2m$ and pair charge = $-2e$.

$$\mathbf{p} = -i\hbar\nabla - \frac{2e}{c}A \quad (107)$$

A current, or a CM momentum \mathbf{K} , modifies the single pair state

$$\psi(\mathbf{r}_1, \mathbf{r}_2) = \frac{1}{L^3} \sum_k g(\mathbf{k}) e^{i\mathbf{k} \cdot (\mathbf{r}_1 + \mathbf{r}_2)/2} e^{i\mathbf{k} \cdot (\mathbf{r}_1 - \mathbf{r}_2)} \quad (108)$$

$$\psi(\mathbf{K}, \mathbf{r}_1, \mathbf{r}_2) = \psi(\mathbf{K} = 0, \mathbf{r}_1, \mathbf{r}_2) e^{i\mathbf{K} \cdot \mathbf{R}} \quad (109)$$

where $\mathbf{R} = \frac{\mathbf{r}_1 + \mathbf{r}_2}{2}$ is the cm coordinate and $\hbar\mathbf{K}$ is the cm momentum. Thus

$$\Phi_{BCS} \simeq e^{i\phi} \Phi_{BCS}(\mathbf{K} = 0) = e^{i\phi} \Phi(0) \quad (110)$$

$$\phi = \mathbf{K} \cdot (\mathbf{R}_1 + \mathbf{R}_2 + \dots) \quad (111)$$

(In principle, we should also antisymmetrize this wave function; however, we will see soon that this effect is negligible). Due to the rigidity of the BCS state it is valid to approximate

$$\nabla = \nabla_R + \nabla_r \approx \nabla_R \quad (112)$$

Thus

$$\mathbf{j}_s \approx \frac{2e}{4m} \sum_\nu \left\{ \Phi_{BCS}^* \left(-i\hbar\nabla_{R_\nu} + \frac{2eA}{c} \right) \Phi_{BCS} + \Phi_{BCS} \left(i\hbar\nabla_{R_\nu} + \frac{2eA}{c} \right)^* \Phi_{BCS}^* \right\} \quad (113)$$

or

$$\mathbf{j}_s = -\frac{2e}{2m} \left\{ |\Phi(0)|^2 \frac{4eA}{c} + 2\hbar |\Phi(0)|^2 \sum_{\nu} \nabla_{R\nu} \phi \right\} \quad (114)$$

Then since for any ψ , $\nabla \times \nabla\psi = 0$

$$\nabla \times \mathbf{j}_s = -\frac{2e^2}{mc} |\Phi(0)|^2 \nabla \times A \quad (115)$$

or since $|\Phi(0)|^2 = \frac{n_s}{2}$

$$\nabla \times \mathbf{j} = -\frac{ne^2}{mc} \mathbf{B} \quad (116)$$

which is the second London equation which as we saw in Sec. 2 leads to the Meissner effect. Thus the second London equation can only be derived from the BCS theory by assuming that the BCS state is spatially homogeneous.

8 Quantization of Magnetic Flux

The rigidity of the wave function (superconducting coherence) also guarantees that the flux penetrating a superconducting loop is quantized. This may be seen by integrating Eq. 114 along a contour within the superconducting bulk (at least a

distance Λ_L from the surface).

$$\mathbf{j}_s = -\frac{e^2 n_s}{mc} A - \frac{e\hbar n_s}{2m} \sum_{\nu} \nabla_{R\nu} \phi \quad (117)$$

$$\oint \mathbf{j}_s \cdot d\mathbf{l} = -\frac{e^2 n_s}{ms} \oint A \cdot d\mathbf{l} - \frac{e\hbar n_s}{2m} \sum_{\nu} \oint \nabla_{R\nu} \phi \cdot d\mathbf{l} \quad (118)$$

Presumably the phase of the BCS state $\Phi_{BCS} = e^{i\phi} \Phi(0)$ is

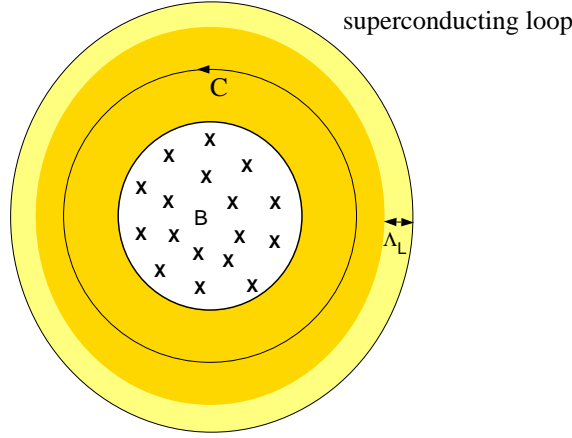


Figure 26: *Magnetic flux penetrating a superconducting loop is quantized. This may be seen by integrating Eq. 114 along a contour within the superconducting bulk (a distance Λ_L from the surface).*

single valued, so

$$\sum_{\nu} \oint \nabla_{R\nu} \phi \cdot d\mathbf{l} = 2\pi N \quad N \in \mathcal{Z} \quad (119)$$

Also since the path l may be taken inside the superconductor by a depth of more than Λ_L , where $\mathbf{j}_s = 0$, we have that

$$\int \mathbf{j}_s \cdot d\mathbf{l} = 0 \quad (120)$$

so

$$-\frac{e^2 n_s}{m s} \int \mathbf{A} \cdot d\mathbf{l} = -\frac{e^2 n_s}{m s} \int \mathbf{B} \cdot d\mathbf{s} = 2N\pi \frac{e\hbar n_s}{2m} \quad (121)$$

Ie., the flux in the loop is quantized.

9 Tunnel Junctions

Imagine that we have an insulating gap between two metals, and that a plane wave (electronic Bloch State) is propagating towards this barrier from the left

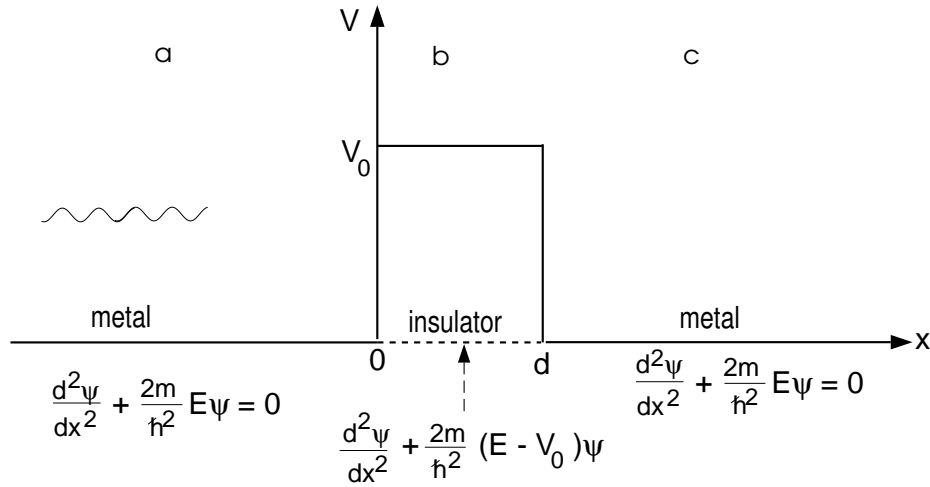


Figure 27:

$$\begin{aligned} \psi_a &= A_1 e^{ikx} + B_1 e^{-ikx} & \psi_b &= A_2 e^{ik'x} + B_2 e^{-ik'x} \\ & & \psi_c &= B_3 e^{-ikx} \end{aligned} \quad (122)$$

These are solutions to the S.E. if

$$k = \frac{\sqrt{2mE}}{\hbar} \quad \text{in a \& c} \quad (123)$$

$$k' = \frac{\sqrt{2m(E - V_0)}}{\hbar} \quad \text{in b} \quad (124)$$

The coefficients are determined by the BC of continuity of ψ and ψ' at the barriers $x = 0$ and $x = d$. If we take $B_3 = 1$ and $E < V_0$, so that

$$k' = i\kappa = \frac{\sqrt{2m(E - V_0)}}{\hbar} \quad (125)$$

then, the probability of having a particle tunnel from left to right is

$$P_{l \rightarrow r} \propto \frac{|B_3|^2}{|B_1|^2} = \frac{1}{|B_1|^2} = \left\{ \frac{1}{2} - \frac{1}{8} \left(\frac{k}{\kappa} - \frac{\kappa}{k} \right)^2 + \frac{1}{8} \left(\frac{k}{\kappa} + \frac{\kappa}{k} \right)^2 \cosh 2\kappa d \right\}^{-1} \quad (126)$$

For large κd

$$P_{l \rightarrow r} \propto 8 \left(\frac{k}{\kappa} + \frac{\kappa}{k} \right)^{-2} e^{-2\kappa d} \quad (127)$$

$$\propto 8 \left(\frac{k}{\kappa} + \frac{\kappa}{k} \right)^{-2} \exp \left\{ -\frac{2d\sqrt{2m(V_0 - E)}}{\hbar} \right\} \quad (128)$$

Ie, the tunneling probability falls exponentially with distance.

Of course, this explains the physics of a single electron tunneling across a barrier, assuming that an appropriate state is filled on the left-hand side and available on the right-hand side. This, as can be seen in Fig. 28, is not always the case, especially in a conductor. Here, we must take into account the densities of states and their occupation probabilities f . We will be interested in applied voltages V which will shift the chemical potential eV . To study the gap we will apply

$$eV \sim \Delta \quad (129)$$

We know that $\frac{2\Delta}{k_B T_c} \sim 4$, $\Delta \sim \frac{4k_B T_c}{2} \sim 10^\circ K$. However typical metallic densities of states have features on the scale of electronvolts $\sim 10^4^\circ K$. Thus, on this energy scale we may approximate

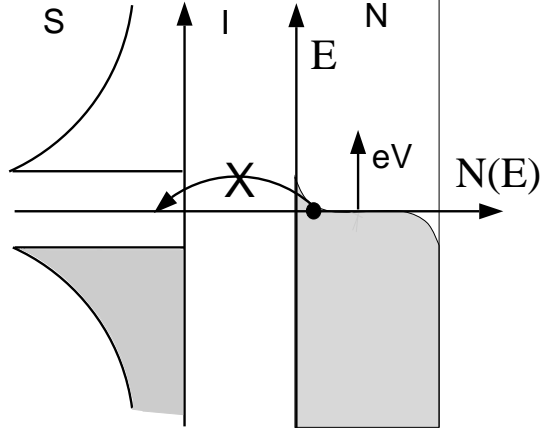


Figure 28: *Electrons cannot tunnel across the barrier since no unoccupied states are available on the left with correspond in energy to occupied states on the right (and vice-versa). However, the application of an appropriate bias voltage will promote the state on the right in energy, inducing a current.*

the metallic density of states as featureless.

$$N_r(\epsilon) = N_{metal}(\epsilon) \approx N_{metal}(E_F) \quad (130)$$

The tunneling current is then, roughly,

$$I \propto P \int d\epsilon f(\epsilon - eV) N_r(E_F) N_l(\epsilon) (1 - f(\epsilon)) - P \int d\epsilon f(\epsilon) N_l(\epsilon) N_r(E_F) (1 - f(\epsilon - eV)) \quad (131)$$

For $eV = 0$, clearly $I = 0$ i.e. a balance is achieved. For $eV \neq 0$ a current may occur. Let's assume that $eV > 0$ and $k_B T \ll \Delta$. Then the rightward motion of electrons is

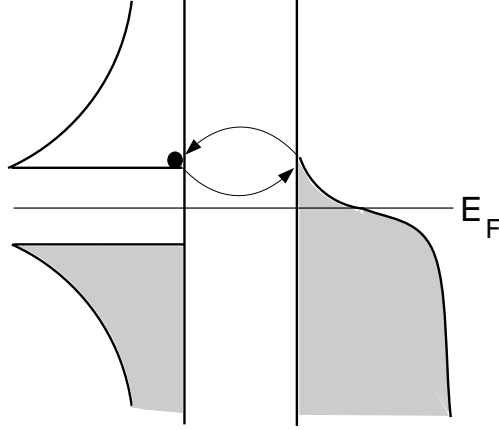


Figure 29: If $eV=0$, but there is a small overlap of occupied and unoccupied states on the left and right sides, then there still will be no current due to a balance of particle hopping.

suppressed. Then

$$I \sim PN_r(E_F) \int d\epsilon f(\epsilon - eV) N_l(\epsilon) \quad (132)$$

and

$$\frac{dI}{dV} \sim PN_r(E_F) \int d\epsilon \frac{\partial f(\epsilon - eV)}{\partial V} N_l(\epsilon) \quad (133)$$

$$\frac{\partial f}{\partial V} \sim e\delta(\epsilon - eV - E_F) \quad (T \ll E_F) \quad (134)$$

$$\frac{dI}{dV} \simeq PN_r(E_F) N_l(eV + E_F) \quad (135)$$

Thus the low temperature differential conductance $\frac{dI}{dV}$ is a measure of the superconducting density of states.

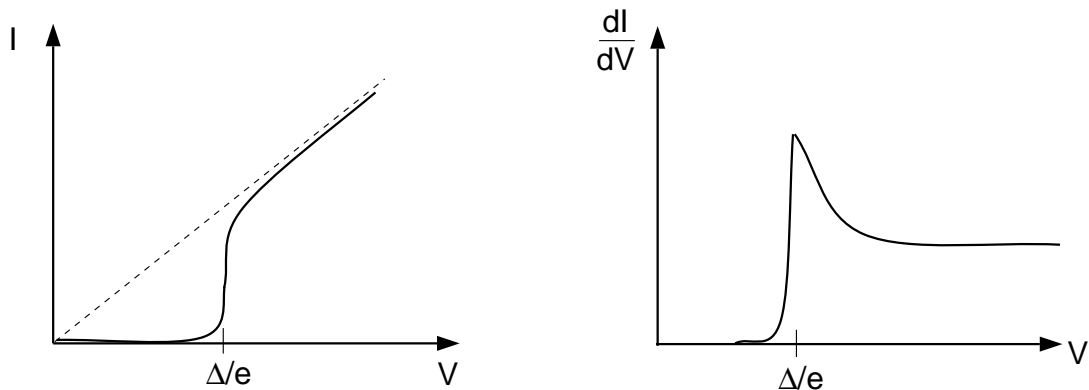


Figure 30: *At low temperatures, the differential conductance in a normal metal-superconductor tunnel junction is a measure of the quasiparticle density of states.*

10 Unconventional Superconductors

From different review articles, it is clear that there are different definitions of unconventional superconductivity. For example, some define it as beyond BCS, or to only include superconductors, such as odd-frequency superconductors, that clearly cannot be described by the BCS equations (although it may be possible to describe them with the Eliashberg equations). Another definition, which I will adopt, is to define unconventional superconductors that are not described by the simple discussion of the BCS equations that we have discussed so far in this chapter. These will include (and will be defined below) triplet, lower symmetry (e.g., d-wave) or often magnetically mediated

superconductors, to very unusual ideas, that have not yet been observed, such as odd-frequency superconductors. In each case, I will assume that the superconducting state is formed via Cooper pairing of fermions, so that the order parameter must remain odd under a product of symmetry operations, such as parity, time reversal, spin, etc. as summarized in Tab. 2.

Type	spin symmetry	inversion symmetry	time reversal symmetry
odd-frequency	triplet (even)	even	odd
odd-frequency	singlet (odd)	odd (p-wave)	odd
d-wave S=0 L=2	singlet (odd)	even	even
triplet S=1 L=1	triplet (even)	odd	even

Table 2: Types and characteristics of the order parameter of unconventional superconductors formed from electron pairs.

Below, we will discuss each of these unconventional superconductors, and identify their properties and experimental signatures.

10.1 D-wave Superconductors

Cuprate superconductors which are nearly antiferromagnetic, and so highly anisotropic that they may be viewed as nearly two-dimensional.

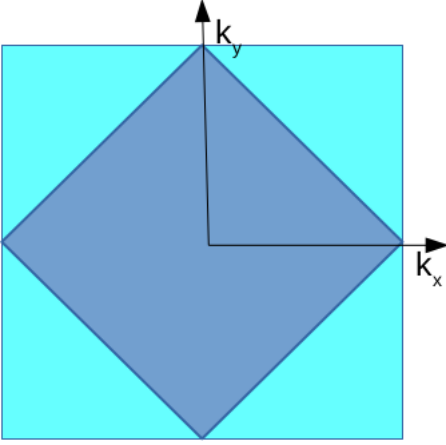


Figure 31: *The Fermi surface of the 2D non-interacting half-filled Hubbard model with near-neighbor hopping. The pairing interactions due to the magnetic correlations are strongest at half filling and on the Fermi surface near the magnetic order vectors $(\pm\pi, \pm\pi)$. Since they are purely repulsive, the order parameter, which is largest in between the ordering vectors (i.e., $(0, \pi)$) must change sign like a d -wave orbital (see text).*

In fact the modeling of Zhang and Rice reduces the cuprates to a 2D t - J or Hubbard model, which are related by a Schrieffer-Wolf transformation, and the models are close to half filling where the non-interacting

fermi surface forms a square as illustrated in Fig. 31 and strong antiferromagnetic correlations begin to form. The latter are believed to provide the pairing interaction, despite the fact that the pairing interaction from antiferromagnetic correlations is purely repulsive.

Whereas conventional s -wave superconductors form spin singlet pairs with s -wave symmetry ($S=0$, $L=0$), d -wave superconductors form lower symmetry pairs ($S=0$, $L=2$). This pairing may be described by the BCS formalism with a k -dependent $\Delta(\mathbf{k})$.

We assume that the pairing interaction is strongly peaked at the antiferromagnetic ordering wavenumbers $\mathbf{k} = (\pm\pi, \pm\pi)$, or $V(\mathbf{k}) = -V_0\delta(\mathbf{k} - (\pm\pi, \pm\pi))$ where $V_0 > 0$ and is only finite at energies near the fermi surface. Since the pairing is due to magnetic correlations, the width of the scattering shell is now roughly J which is assumed to be $J \ll E_F$. In this case the gap equation becomes

$$\Delta(\mathbf{k}') = \frac{1}{2L^3} \sum_k \frac{\Delta(\mathbf{k})V(\mathbf{k} - \mathbf{k}')}{\sqrt{\xi_k^2 + \Delta(\mathbf{k})^2}} \quad (136)$$

In order to have a solution, the minus sign in V must be canceled. The large contributions to the sum comes when $\mathbf{k} - \mathbf{k}'$ is a magnetic ordering vector where V is large. Suppose $\mathbf{k} - \mathbf{k}' = (\pi, \pi)$, and $\mathbf{k} = (\pi, 0)$ and $\mathbf{k}' = (0, -\pi)$, then to cancel the minus sign, we need $\Delta(\mathbf{k}) = -\Delta(\mathbf{k}')$, so that the order parameter changes sign for every rotation by $\pi/2$ and presumably is zero along the diagonal, just like a $d_{x^2-y^2}$ orbital. Hence the name d-wave superconductivity.

Note that the lower symmetry of the order parameter has experimental consequences. First the d-wave geometry of the order parameter may be directly confirmed by creating a tun-

nel junction with a conventional s-wave superconductor, as illustrated in Fig. 32.

Here, the phase difference across one of the s-d junctions causes a persistent current and a trapped magnetic flux measurable by a SQUID. d-wave superconductivity is very sensitive to disorder, such as Zn doping for Cu

where only a few percent of impurities can destroy superconductivity.

The reason for this sensitivity is that

the elastic scattering from the Zn impurities is nearly local, and hence mixes $\Delta(\mathbf{k})$ with all other \mathbf{k} values on the fermi surface, and when averaged over the fermi surface, the order parameter is zero. Furthermore since the gap has a range of values extending to zero, so do the excitations across the gap. As a result, the activated T-dependence seen in the specific heat is replaced by algebraic or power-law T-dependence seen in the nuclear magnetic resonance relaxation rate and specific heat.

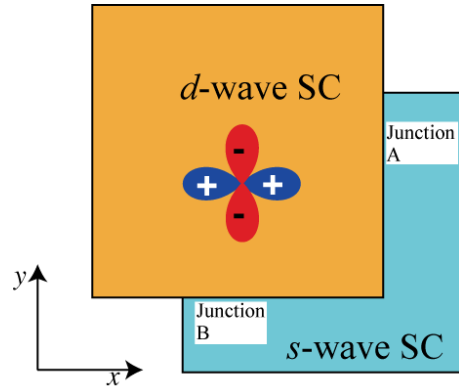


Figure 32: *Cartoon of a corner junction between a conventional s-wave and a d-wave, cuprate, superconductor.*

10.2 Triplet Superconductors

As illustrated in Tab. 2, triplet superconductivity is also possible which is even in spin or odd in orbital symmetry. More complex triplet states are also possible, but will not be discussed here. Triplet superconductivity may actually be an old subject if it include condensation of ^3He which is spin 1/2 and forms a triplet condensate which is not a superconductor since ^3He carries no charge. as ($S=1, L=1$). The pairing is believed to be mediated by magnetic fluctuations enhanced by the proximity to a ferromagnetic transition (similar to the case for the cuprates where the magnetic fluctuations are enhanced by proximity to half filling). It is believed that the triplet state is favored by the exchange hole that keeps the pair of electrons apart, avoiding the short ranged repulsive interaction between them.

In addition to ^3He triplet superconductivity, with a real supercurrent, is believed to exist in a number of solids, including Sr_2RuO_4 which is believed to have a chiral p-wave state and a complex gap function which breaks time-reversal so that the pairs have a finite magnetic moment.

This triplet state should have a number of experimental consequences. Perhaps the most obvious is that, like the d-wave superconductors, the pairing should be very sensitive to disorder, at least disorder with a mean-free path that is shorter than the pairing length. I.e., the stronger the pairing, the less sensitive the state is to disorder.

10.3 Odd-frequency Superconductors

Another, not yet observed (to the best of my knowledge) type of pairing is odd in frequency or in time. In this case both the spin and orbital part of the pairing can be even or both odd. Of course, it is difficult to treat such a state in the BCS formalism since the frequency-dependence of the order parameter is suppressed.